

Development of Eco Friendly Cement Concrete Using Ground Granulated Blastfurnace Slag

K.Kathiresan,

Assistant professor, Department of Civil Engineering,
J.K.K.Munirajah College of Technology,
Erode-638506, Tamilnadu, India.
kathir2me@gmail.com

G.Vennila,

Professor, Department of Civil Engineering,
K.S. Rangasamy College of Technology,
Namakkal-637215, Tamilnadu, India.
vennilajagan@gmail.com

Abstract—Cement is the most commonly used construction material. Now a days, cement production is increasing rapidly. In order to minimize the production and usage of cement, an alternative solution is to be implemented as either or partial replacement of cement. GGBS is the waste byproduct produced during the manufacturing of Steel. GGBS is used as a replacement for cement for every 5% and the optimum mix is found out by studying the mechanical properties. Replacement of GGBS was carried out up to 50% against cement. Presence of GGBS in the concrete mix exhibit notable achievement in the compressive strength of the concrete, however presence of GGBS reduce the performance of concrete in split tensile stress and flexural stress due to increase in brittleness of the material. Modulus of elasticity of GGBS concrete shows prominent performance when compared with the conventional concrete. From the above these mixes, GGBS with 45% replacement against cement in concrete shows the better performance..

Keywords— GGBS, Concrete, Mechanical Properties, Steel Slag.

I. INTRODUCTION

India is the second largest producer of cement next to china. According to recent survey, it was found that cement requirement will rise 550 to 600 million tonnes per annum by the year 2025. Cement Production in cement industry is the major cause of global warming which liberates carbon dioxide[1, 2]. In order to reduce the global warming and to decrease the cement and aggregates in concrete, the alternatives is to be used used like GGBS, Steel Slag, Flyash etc., [3, 4] Granulated Blast Furnance Slag Known as GGBS are the by product of blast furnace which is delivered during the manufacture process of iron. The iron are operate at 1500 deg Celsius and are quenched in large volume of water to form molten glassy materials and are further crushed to form powdered material known as GGBS. GGBS is used as a replacement for cement in concrete[5, 6]. Due to the usage of GGBS in cement, the production and usage of cement in concrete can be reduced to a considerable quantity[7]. Steel slag is the by product when lime is added to extract impurities during steel manufacturing process and it amounts about 15-20% of crude steel production[8, 9]. The application of steel slag includes producing metallurgical raw materials, road construction works, innovative building materials, environmental and also in agricultural fields. However, the application of steel slag in concrete is still minimum [10-13]. Steel slag is used as a replacement for aggregates. In our study, we are going to used GGBS as replacement for Cement, Finely grained Steel Slag as replacement for Fine aggregate and Coarsely grained Steel Slag as replacement for Coarse aggregate in concrete.

II. METHODS & MIXTURE

Cement

OPC of 53 grade conforming to IS 12269 [14] was used in this study. The Chemical composition of Cement is Shown in Table 1. River sand used as fine aggregate with specific gravity of 2.65 and 10 mm and 20mm stone extracted from the quarry was used as a coarse aggregate with specific gravity of 2.8.

TABLE 1: CHEMICAL COMPOSITION OF CEMENT

%	CaO	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	MgO	SO ₃	Alkalines
Cement	63.71	22.3	4.51	3.39	1.77	2.59	1.73

Ground Granulated Blast Furnace Slag

Ground Granulated Blast furnace Slag (GGBS) is a byproduct from the blast furnaces used to make iron. These operate at a temperature of about 1500 degrees centigrade and are fed with a cautiously controlled mixture of iron ore, coke and limestone. The iron ore is reduced to iron and the left over materials from a slag is floated on top of the iron. This slag is sometimes tapped off as a molten liquid and if it is to be used for the manufacture of GGBS it has to be rapidly satisfied in large volumes of water. The satisfying increases the cementitious properties and produces granules similar to coarse sand. This granulated slag is after that dried and ground to a powder.

Steel Slag

Steel slag is a by-product of the conversion of iron to steel process and it presents differences depending on the raw materials and process. Fifty million tons per year of steel slag are produced as a residue in the world. Owing to the intensive research work during the last 30 years, today about 65% of the produced steel slags are used on qualified fields of application. But the remaining 35% of these slags are still dumped. This Steel slag is crushed into pieces and used as a fine and coarse aggregate along with conventional fine and coarse aggregate.

TABLE 2: Mix

Mix Designation	Cement (kg/m ³)	GGBS	Course Agg (kg/m ³)		Fine Agg (kg/m ³)	Silica Fume (kg/m ³)	Water/Cement	Super Plasticizer (%)
			10 mm	20 mm				
CC	415	--	514	770	653	83	0.34	1.2
GGBSI	394.25	20.75	514	770	653	83	0.34	1.2
GGBSII	373.5	41.5	514	770	653	83	0.34	1.2
GGBSIII	352.75	62.25	514	770	653	83	0.34	1.2
GGBSIV	332	83	514	770	653	83	0.34	1.2
GGBSV	311.25	103.75	514	770	653	83	0.34	1.2
GGBSVI	290.5	124.5	514	770	653	83	0.34	1.2
GGBSVII	269.75	145.25	514	770	653	83	0.34	1.2
GGBSVIII	249	166	514	770	653	83	0.34	1.2
GGBSIX	228.25	186.75	514	770	653	83	0.34	1.2
GGBSX	207.5	207.5	514	770	653	83	0.34	1.2

III. EXPERIMENTAL INVESTIGATION

The mix design of this investigation is obtained by the following mechanical properties.

Compressive Strength

Compressive strength is the capability of concrete material to take the compressive or flexural loads on its face without any deformation and cracks in the material. For this investigation 150 mm x 150 mm x 150 mm size cubes were used to study the performance of different concrete mixes under compression after 28 days curing in a room temperature. 100 Tonne compressive strength testing machine was used for this investigation and test was carried as per IS standards. For each mix three cubes were used for compression test.

Split Tensile Strength

Split tensile strength is one of the important properties of concrete material, since concrete is weak in tension owing to its brittle in nature. For this study cylindrical specimen of diameter 150 mm and 300 mm height is used for this investigation. Cylinder is place horizontal on the compression testing machine and load load was applied along the length to split the specimen. Formula given below was used to determine the split tensile stress of specimen, where P is the applied load, L is the length of the cylinder specimen, d is the diameter of cylinder.

Split Tensile Strength, $T = 2P/(\pi Ld)$

Flexural Strength

To evaluate the tensile strength of concrete indirectly flexural strength test setup was used. This is also called as modulus of rupture. Specimen of size 100 mm x 100 mm cross section and 500 mm length prism was used for this study. After 28 days curing specimen was subjected to investigation under flexural testing machine, clear span of the specimen is 450 mm and two point load was applied at every 150 mm.

Flexural Strength, $F = (P*L)/(bd^2)$

Above formula is used for determine the flexural stress in the concrete, P is the applied load, L is the span between the support, b and d is the breadth and depth of the specimen respectively.

Modulus of Elasticity

Cylinder specimen of size 150 mm diameter and 300 mm length is used to determine the modulus of elasticity of concrete, this test provide the performance of hardened properties of cement paste with the coarse aggregate. Compressometer is used to determine the strain in the concrete and it is placed in the center portion of length of the cylinder and dial gauge present in the compressometer provides the contraction of specimen under compressive load.

IV. RESULTS AND DISCUSSION

Compressive Strength

Compressive Strength GGBS based concrete mixes are shown in the Figure 1. From the figure it was observed that the mix with 45% of GGBS performed better in compressive strength. Conventional concrete mix CC exhibit the compressive strength of 53.1 MPa, similarly mix GGBS9 exhibit 54.5 MPa. GGBS is replaced against the cement with the increment of 5% and stopped up to 50%, since the strength reduced after 45% replacement. 51.3 MPa, 52.1 MPa, 52.1 MPa, 52.4 MPa, 52.7 MPa, 52.9 MPa, 53.3 MPa, 53.9 MPa and 52.3 MPa are the compressive strength of concrete for GGBS1, GGBS2, GGBS3, GGBS4, GGBS5, GGBS6, GGBS7, GGBS8 and GGBS10 mixes respectively. Presence of GGBS improves the performance of the concrete under compressive strength, since 3.5% is the lowest strength of GGBS concrete from the conventional concrete strength.

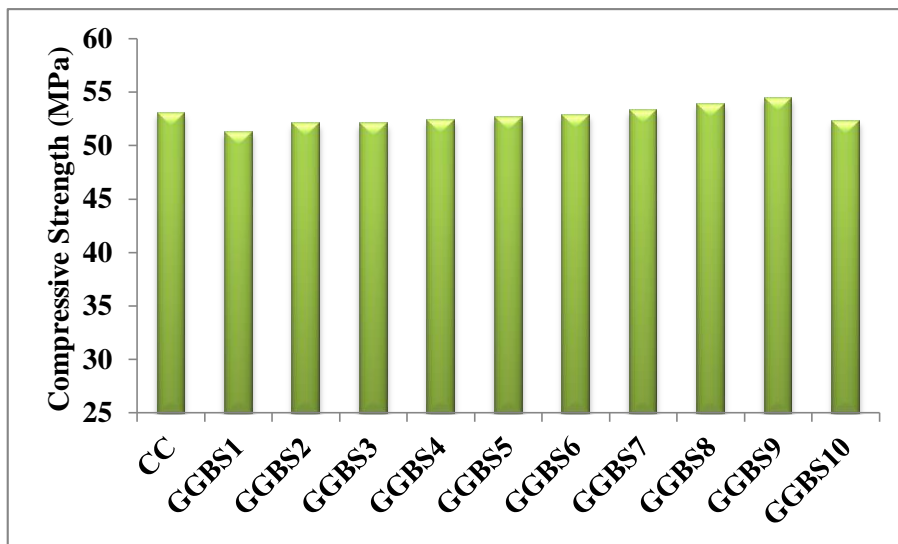


Figure 1. Compressive Strength of GGBS based Concrete

Split Tensile Strength

Split tensile strength of concrete is show in the Figure.2, from the results it was observed that presence of GGBS decrease the split tensile strength of the concrete. 5.21 MPa was the split tensile strength of conventional concrete, which is greater than 4.7%, 3.2%, 3.8%, 4.6%, 5.3%, 5.3%, 6.3%, 6.8%, 7.4% and 13.3% for the mixes for GGBS1, GGBSII, GGBSIII. GGBSIV, GGBSV, GGBSVI, GGBSVII, GGBSVIII, GGBSIX and GGBSX mixes respectively. In the results it is observed that the presence of GGBS reduces the split tensile strength of concrete having notable compressive strength, this shows that split tensile strength decreases with increases in GGBS content in the concrete. Brittleness of concrete was improved due to the presence of GGBS in the concrete mixes. Figure 3. Shows the regression analysis of Split Tensile Strength vs Compressive Strength. From the regression investigation it was observed that the experimental values and predicted model values are exhibit similar results in the mixes.

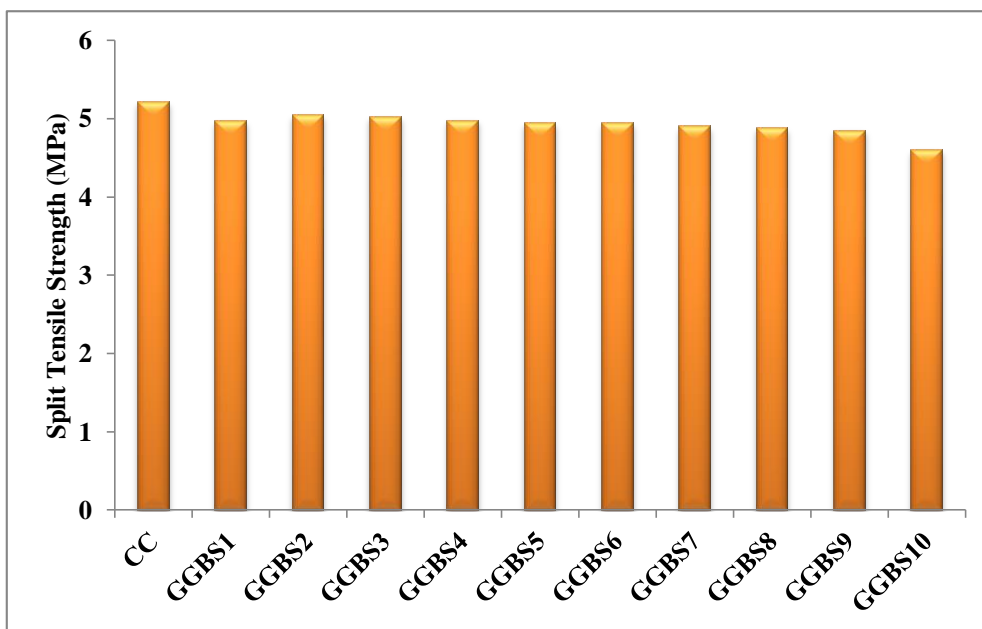


Figure 2. Split Tensile Strength of GGBS based Concrete

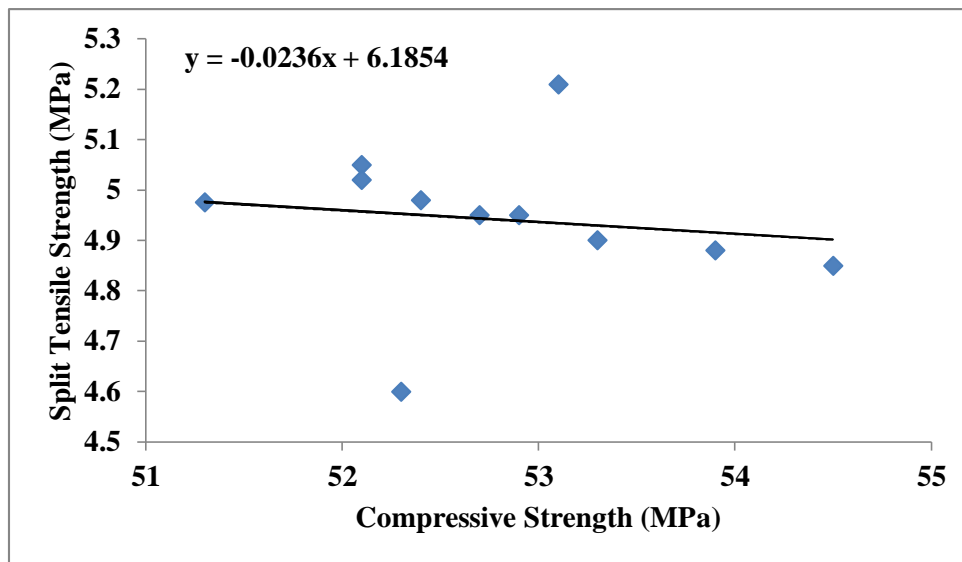


Figure 3. Regression Analysis of Split Tensile Strength vs Compressive Strength

Flexural Strength

Flexural Strength of the concrete is shown in figure 4. On analyzing the results, it is found that the GGBS influences the flexural strength of concrete. With the addition of GGBS, the strength of concrete decreases simultaneously. The flexural strength of conventional concrete is 4.87MPa, however the flexural strength of GGBS1, GGBS2, GGBS3, GGBS4, GGBS5, GGBS6, GGBS7, GGBS8, GGBS9 and GGBS10 mixes are 4.70MPa, 4.78MPa, 4.78MPa, 4.74MPa, 4.71MPa, 4.66MPa, 4.66MPa, 4.63MPa, 4.62MPa, 4.6MPa respectively. Figure 5 shows the regression analysis of flexural strength vs compression strength. From the regression analysis, it is found that experimental values are almost similar to the predicted values.

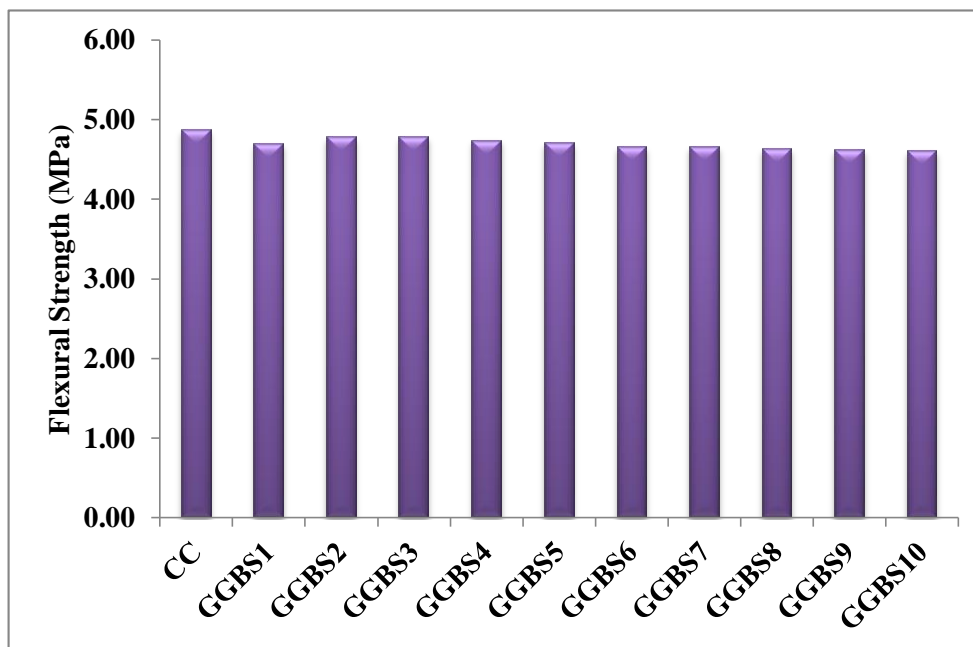


Figure 4. Flexural Strength of GGBS based Concrete

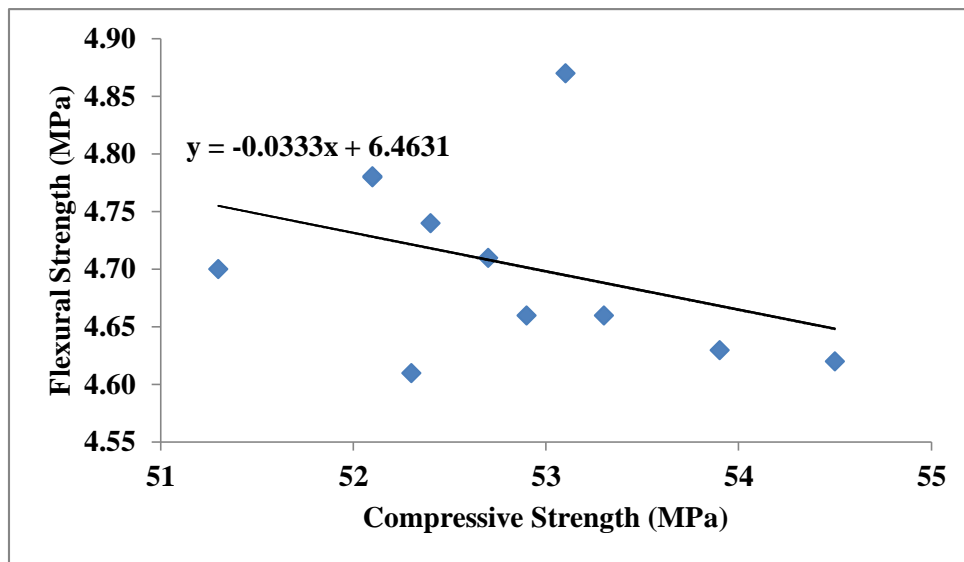


Figure 5. Regression Analysis of Flexural Strength vs Compressive Strength

Modulus of Elasticity

Modulus of Elasticity of GGBS based concrete mixes are shown in the Figure 6. From the figure it was observed that the mix with 45% of GGBS performed better in Modulus of Elasticity. Modulus of Elasticity of mix GGBS9 is 2.97% greater than conventional concrete. GGBS is replaced against the cement with the increment of 5% and stopped up to 50%, since the strength reduced after 45% replacement. Figure 7 shows the regression analysis of modulus of elasticity vs compression strength. From the regression analysis, it is found that experimental values are almost similar to the predicted values.

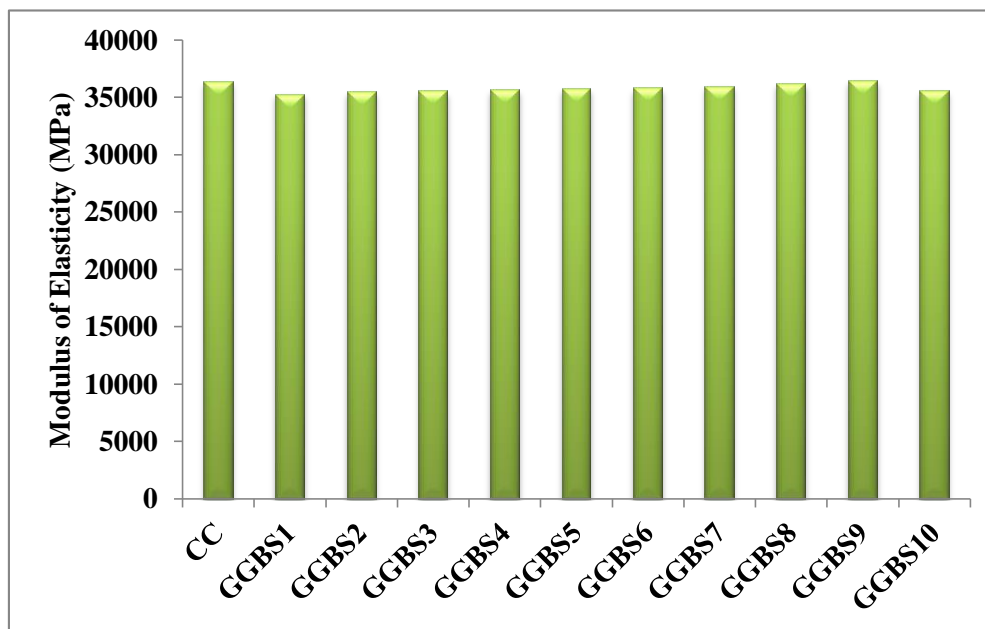


Figure 6. Modulus of Elasticity of GGBS based Concrete

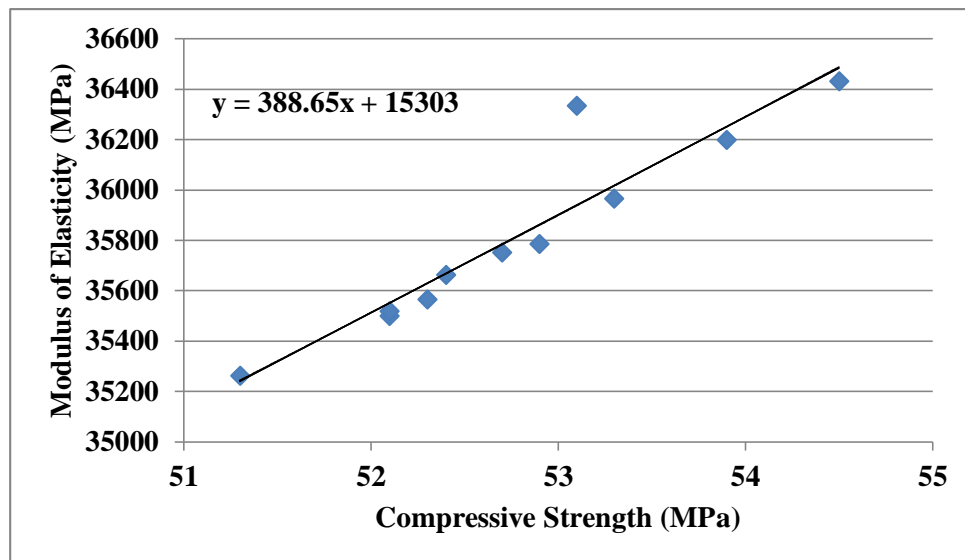


Figure 7. Regression Analysis of Modulus of Elasticity vs Compressive Strength

V. CONCLUSION

An experimental study was carried out to investigate the effect of GGBS in split tensile strength, flexural strength, compressive strength and modulus of elasticity of concrete. The following conclusion is made

- Compressive strength of GGBS concrete performed better than the conventional concrete and 45% GGBS (Mix GGBS IX) replaced concrete exhibit more strength.
- Performance of GGBS concrete in split tensile strength and flexural strength is not as expected level. Presence of GGBS reduces the indirect tensile strength of concrete due to its brittleness nature.
- In case of modulus of elasticity the harden gel formation of GGBS concrete was better than the conventional concrete, similar to the compressive strength concrete with 45% GGBS (Mix GGBS IX) exhibits better performance.

References

- [1]. Schneider, M., et al., "Sustainable cement production—present and future". *Cement and concrete research*, Vol. 41 Iss. 7, pp. 642-650, 2011.
- [2]. Liu, Z., et al., "Reduced carbon emission estimates from fossil fuel combustion and cement production in China". *Nature*, Vol. 524, Iss. 7565, pp. 335, 2015.
- [3]. Davidovits, J., "Global warming impact on the cement and aggregates industries". *World resource review*, Vol. 6, Iss. 2, pp. 263-278, 1994.
- [4]. Chen, C., et al., "Environmental impact of cement production: detail of the different processes and cement plant variability evaluation". *Journal of Cleaner Production*, Vol. 18, Iss. 5, pp. 478-485, 2010.
- [5]. Oner, A. and S. Akyuz, "An experimental study on optimum usage of GGBS for the compressive strength of concrete". *Cement and Concrete Composites*, Vol. 29, Iss. 6, pp. 505-514, 2007.
- [6]. Babu, K.G. and V.S.R. Kumar, "Efficiency of GGBS in concrete". *Cement and Concrete Research*, Vol. 30, Iss. 7, pp. 1031-1036, 2000.
- [7]. Arivalagan, S., "Sustainable studies on concrete with GGBS as a replacement material in cement". *Jordan journal of civil Engineering*, Vol. 159, Iss. 3147, pp. 1-8, 2014.
- [8]. Cheng, A., et al., "Influence of GGBS on durability and corrosion behavior of reinforced concrete". *Materials Chemistry and Physics*, Vol. 93, Iss. 2-3, pp. 404-411, 2005.
- [9]. Tsakiridis, P., et al., "Utilization of steel slag for Portland cement clinker production". *Journal of Hazardous Materials*, Vol. 152, Iss. 2, pp. 805-811, 2008.
- [10]. Shen, W., et al., "Investigation on the application of steel slag–fly ash–phosphogypsum solidified material as road base material". *Journal of hazardous materials*, Vol. 164, Iss. 1, pp. 99-104, 2009.

- [11]. Geiseler, J., "Use of steelworks slag in Europe". *Waste management*, Vol. 16, Iss. 1-3, pp. 59-63, 1996.
- [12]. McNally, C. and E. Sheils, "Probability-based assessment of the durability characteristics of concretes manufactured using CEM II and GGBS binders". *Construction and Building Materials*, Vol. 30, pp. 22-29, 2012.
- [13]. Shi, C., "Steel slag—its production, processing, characteristics, and cementitious properties". *Journal of Materials in Civil Engineering*, Vol. 16, Iss. 3, pp. 230-236, 2004.
- [14]. IS:12269, "Ordinary Portland Cement, 53 Grade - Specification". Bureau of Indian Standard New Delhi, 2013.